

Conductivity Evaluation of a Newly Proposed Material for a SAR Reflector Antenna

저자 (Authors)	Seong Sik Yoon, Jae Wook Lee, Taek Kyung Lee, Jin Ho Roh, Hark Inn Kim, Dong Woo Yi
출처 (Source)	Journal of Electromagnetic Engineering And Science <u>14(3)</u> , 2014.9, 293-298 (6 pages)
발행처 (Publisher)	한국전자파학회 Koea Electromagnetic Engineering Society
URL	http://www.dbpia.co.kr/Article/NODE02481780
APA Style	Seong Sik Yoon, Jae Wook Lee, Taek Kyung Lee, Jin Ho Roh, Hark Inn Kim, Dong Woo Yi (2014). Conductivity Evaluation of a Newly Proposed Material for a SAR Reflector Antenna. <i>Journal of Electromagnetic Engineering And Science</i> , 14(3), 293-298.
이용정보 (Accessed)	한국항공대학교 203.253.***.125 2018/01/04 15:50 (KST)

저작권 안내

DBpia에서 제공되는 모든 저작물의 저작권은 원저작자에게 있으며, 누리미디어는 각 저작물의 내용을 보증하거나 책임을 지지 않습니다. 그리고 DBpia에서 제공되는 저작물은 DBpia와 구독 계약을 체결한 기관소속 이용자 혹은 해당 저작물의 개별 구매자가 비영리적으로만 이용할 수 있습니다. 그러므로 이에 위반하여 DBpia에서 제공되는 저작물을 복제, 전송 등의 방법으로 무단 이용하는 경우 관련 법령에 따라 민, 형사상의 책임을 질 수 있습니다.

Copyright Information

Copyright of all literary works provided by DBpia belongs to the copyright holder(s) and Nurimedia does not guarantee contents of the literary work or assume responsibility for the same. In addition, the literary works provided by DBpia may only be used by the users affiliated to the institutions which executed a subscription agreement with DBpia or the individual purchasers of the literary work(s) for non-commercial purposes. Therefore, any person who illegally uses the literary works provided by DBpia by means of reproduction or transmission shall assume civil and criminal responsibility according to applicable laws and regulations.

Conductivity Evaluation of a Newly Proposed Material for a SAR Reflector Antenna

Seong Sik Yoon¹ · Jae Wook Lee^{1,*} · Taek Kyung Lee¹ · Jin Ho Roh² · Hark Inn Kim² · Dong Woo Yi³

Abstract

Large spaceborne antennas should be lightweight, a factor related to the development costs of launch vehicles. In order to overcome this drawback, a feasibility study of a new carbon fiber reinforced polymer (CFRP) named M55J/RS3 is carried out for a synthetic aperture radar (SAR) reflector antenna. In particular, the high resolution of detected images is taken into consideration. To validate the electrical performance, a test of the CFRP specimen is fabricated, and the transmission/reflection coefficients are measured using a standard X-band waveguide. Finally, the effective complex permittivity and effective electrical conductivity are derived from the obtained measured data. By applying the derived conductivity to the simulation of the radiation pattern, antenna gain, and beamwidth-instead of relying on the assumption of a perfect electric conductor-variations in electrical performance are also investigated and discussed.

Key Words: CFRP, Complex Permittivity, Electric Conductivity, Gain Loss, Reflector Antenna.

I. INTRODUCTION

Composite materials consisting of two or more constituents are intentionally combined to form heterogeneous structures having new electrical and mechanical characteristics. These materials can be categorized into several types of composites depending on the structures of the reinforced materials, e.g., fiber-reinforced and particle-reinforced composite materials. Some common fiber candidates are glass, carbon, graphite, ceramic, and aramid. In addition, suggested matrix types include polymer, metal, and ceramic/glass. The matrix plays an important role in fixing the reinforced material and determining the external pressure distribution [1]. Among these composite materials, carbon fiber reinforced polymer (CFRP) composites are widely used in shipbuilding, aerospace, and aeronautical devices, as they are lightweight and very strong. They also have a high modulus and are insusceptible to corrosion.

In particular, it is well-known that the reflector antenna for

a satellite's synthetic aperture radar (SAR), which requires high gain characteristics, may take up much space and be relatively heavy. An increase in payload weight and low-packaging efficiency relative to the waveguide or patch-typed antenna might cause an increase in the development costs. Hence, new composite materials are essential for a stable lightweight antenna that satisfies the electrical and mechanical performance needs in space environments. Many researchers have studied and investigated satellite antenna applications for newly designed advanced composite materials. For instance, the TDRSS communication satellite employs a graphite fiber-enforced rib in a parabolic dish antenna design with a diameter of 4.8 m. Another example is the 2002M graphite/epoxy applied to the reflector dish truss tube of a multi-purposed Application Technology Satellite launched by the National Aeronautics and Space Administration (NASA) in the United States. As these examples show, the development of composite material application technologies for large-scaled space antennas is now

Manuscript received June 13, 2014 ; Revised September 5, 2014 ; Accepted September 11, 2014. (ID No. 20140613-026J)

¹Department of Electronics, Telecommunication and Computer Engineering, Korea Aerospace University, Goyang, Korea.

²Department of Mechanical Engineering, Korea Aerospace University, Goyang, Korea.

³Agency for Defense Development, Daejeon, Korea.

*Corresponding Author: Jae Wook Lee (e-mail: jwlee1@kau.ac.kr)

This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/3.0>) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

© Copyright The Korean Institute of Electromagnetic Engineering and Science. All Rights Reserved.

being accelerated with a focus on reducing weight [2]. As a composite material candidate, CFRP has also received a lot of attention [3–5]. However, to the best of our knowledge, there is a lacuna in the literature on CFRP electrical performance for satellite antennas, particularly regarding the importance of reliability and experience. In this article, we propose a measurement algorithm for the effective conductivity of an employed composite material called M55J/RS3 to confirm the applicability of the material for an SAR reflector antenna. In addition, we determine the radiation pattern of the reflector antenna using the proposed composite material as a reflector with commercially available software based on the ray tracing method. Section II summarizes the basic theory for the characteristic analysis of the employed CFRP specimen. In Section III, the measured and simulated reflection and transmission coefficients of the target specimen are listed by applying a 22.86 mm × 10.16 mm standard rectangular waveguide WR90. Finally, Section IV shows the radiation behavior with simulated results using the obtained conductivity, and Section V offers our conclusions.

II. A REVIEW OF BASIC THEORY

1. Calculating an Algorithm for Complex Permittivity

By employing a TEM-mode wave propagation between annular disks, it might be possible to obtain the effective complex permittivity and permeability using data related to reflection and transmission [6]. However, for easy fabrication and measurement, WR90 standard waveguides for X-bands are used to measure the electrical parameter values, as shown in Fig. 1. The equations describing the relationship between the reflection coefficient and propagation constant are as follows [7].

$$\Gamma = \frac{\gamma_0 - \gamma_s}{\gamma_0 + \gamma_s} \quad (1)$$

$$\gamma_0 = j \frac{2\pi}{\lambda_0} \sqrt{1 - \left(\frac{\lambda_0}{\lambda_c}\right)^2} \quad (2)$$

$$\gamma_s = j \frac{2\pi}{\lambda_0} \sqrt{\varepsilon' - j \frac{\sigma}{\varepsilon_0 \omega} - \left(\frac{\lambda_0}{\lambda_c}\right)^2} \quad (3)$$

where λ_0 and λ_c represent the wavelength in air and the cutoff wavelength in the used waveguide, respectively. In this work, the complex permittivity ε_s of the employed CFRP specimen indicates.

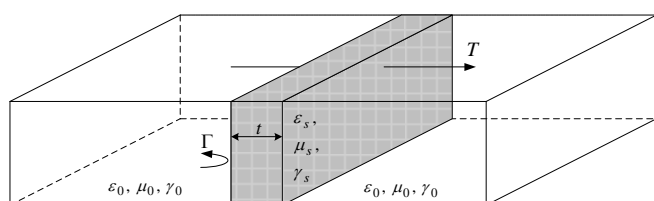


Fig. 1. Description of a CFRP specimen in a rectangular waveguide.

$$\varepsilon_s = \varepsilon' - j\varepsilon'' = \varepsilon' - j \frac{\sigma}{\varepsilon_0 \omega} \quad (4)$$

Hence, the total reflection and transmitted coefficients taking into account multiple reflection can be obtained as follows [6].

$$S_{11}(\omega) = \frac{(1 - e^{-2\gamma_s t})\Gamma}{1 - \Gamma^2 e^{-2\gamma_s t}} \quad (5)$$

$$S_{21}(\omega) = \frac{(1 - \Gamma^2)e^{-\gamma_s t}}{1 - \Gamma^2 e^{-2\gamma_s t}} \quad (6)$$

$$\Gamma = X \pm \sqrt{X^2 - 1}, \quad \text{where } X = \frac{S_{11}^2 - S_{21}^2 + 1}{2S_{11}} \quad (7)$$

$$e^{-\gamma_s t} = \frac{S_{11} + S_{21} - \Gamma}{1 - (S_{11} + S_{21})\Gamma} \quad (8)$$

Through rigorous mathematical manipulations, the final complex permittivity and permeability can be described in detail, as follows.

$$K^2 = -\left\{ \left(\frac{1}{2\pi t} \right) \ln \left(e^{\gamma_s t} \right) \right\}^2 \quad (9)$$

$$\mu_s = \frac{(1 + \Gamma)K}{(1 - \Gamma) \sqrt{\frac{1}{\lambda_0^2} - \frac{1}{\lambda_c^2}}} \quad (10)$$

$$\varepsilon_s = \frac{\lambda_0^2}{\mu_s} \left(\frac{1}{\lambda_c^2} + K^2 \right) \quad (11)$$

2. Calculating an Algorithm for Electrical Conductivity

According to [6], complex permittivity is derived from reflectivity, transmission, and phase differences. However, a composite material having a high reflection coefficient leads to a significant fluctuation in the phase variation of the measured transmission coefficient because of the small $|S_{21}|$ magnitude. In this section, a method is introduced to derive the characteristics of lossy composite materials—materials having a loss tangent higher than 1 [8]. In this case, thickness t is assumed to be larger than the skin depth of the given material. The relationship between the measured S -parameters and the surface impedance of the target material is as follows [7].

$$Z_s = (1 + j) \sqrt{\frac{\pi \mu_0 f}{\sigma}} \quad (12)$$

$$S_{11} = |S_{11}| e^{j\varphi} = \frac{Z_s - Z_w}{Z_s + Z_w} \quad (13)$$

where f means the used frequency, and Z_s and Z_w indicate the surface impedance of the composite material and the wave impedance of the employed waveguide, respectively. The above

equations result in the derivation of the conductivity, as follows.

$$\sigma = 4\pi\mu_0 f \frac{(1 - |S_{11}|^2)^2}{Z_w^2 \left((1 + |S_{11}|^2) - \sqrt{-|S_{11}|^4 + 6|S_{11}|^2 - 1} \right)^2}. \quad (14)$$

III. MEASUREMENTS AND VERIFICATION

In general, the radiation efficiency of a reflector antenna with a central dish depends on the employed material of the dish. In order to achieve a high radiation efficiency, a composite material with a high conductivity should be adopted. The characteristics of composite materials like CFRP usually depend on the inside structure and the manufacturing process. For instance, the CFRP proposed in this paper is fabricated using an autoclave and oven. This hardens and laminates the employed M55J/RS3 prepreg material. The layered direction of the carbon fiber inside the CFRP is defined as a relatively unidirectional angle (0° , 45° , and 90°) to the direction of the electric field inside the transmission waveguide. Fig. 2 shows a measurement setup and a magnified view inside the proposed antenna M55J/RS3 prepreg material using a microscope.

The operating frequency is 9.6 GHz, and the cutoff frequency of the used waveguide ($22.86 \text{ mm} \times 10.16 \text{ mm}$ WR90) for material measurement is 6.56 GHz. Agilent N5230 PNA is employed to take measurements, and X-band through-reflect-line (TRL) calibration is considered. Before the measurement of the fabricated antenna specimen, a test procedure for the validation of the given algorithm is examined with the dielectric specimen having well-known material data. As shown in Table

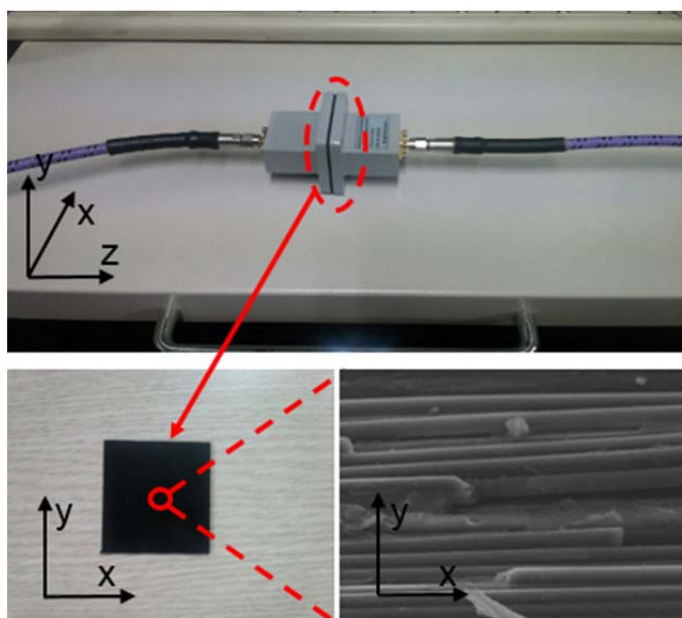


Fig. 2. The measurement setup and the alignment of the carbon fiber inside the 90° carbon fiber reinforced polymer.

Table 1. Applied results of the algorithm extracting the complex permittivity of well-known materials

Material type	Parameter	Real value	Simulated and calculated result	Measured and calculated result
FR-4	Relative permittivity	4.3-	4.29-	4.44-
	Loss tangent	$j0.1$	$j0.11$	$j0.14$
RO-3010	Relative permittivity	10.5-	10.48-	10.36-
	Loss tangent	$j0.037$	$j0.037$	$j0.05$

1, an employed dielectric specimen with complex permittivities of $4.3-j0.1$ and $10.5-j0.037$ and a thickness of 1.2 mm is used. As seen in Table 1, in order to obtain the parameter values of an unknown material, well-known parameter values are adopted for an EM-full simulation, and they are then compared with real values.

For measurement convenience and fabrication ease, the sampled CFRP specimen has a dimension of $4 \times 4 \text{ cm}^2$, which is a little larger than the aperture of the waveguide used for the electrical measurement of the unknown CFRP material. In order to verify the complex permittivity calculating algorithm, a commercially available material having well-known data is employed, measured, and analyzed. As shown in Table 1, the employed substrates for the test have complex permittivities of $4.3-j0.1$ and $10.5-j0.037$, respectively. From the simulation data and measurements in conjunction with the prediction algorithm, we obtain reasonably predictable results showing good agreement with the well-known real values.

The reason for the small discrepancy in the imaginary portion is thought to be the electromagnetic leaky wave and the surface roughness. This stems from the different sizes between the sampled specimen and the aperture, as well as from the tolerance in the etching process.

Table 2 summarizes four electrical characteristics-reflection,

Table 2. The electrical performances of a test CFRP specimen and the evaluated conductivity

	S_{11}	S_{21}	Relative permittivity	Electric conductivity (S/m)
0°	0.993	0.0008	-	12,953
	$\angle -179$	$\angle \text{ND}$		
45°	0.988	0.0006	-	4,385
	$\angle 179$	$\angle \text{ND}$		
90°	0.824	0.189	23.36-j25.91	13.83
	$\angle -178$	$\angle -49.5$		

CFRP = carbon fiber reinforced polymer, ND = not defined.

transmission, permittivity, and conductivity—that arise from the application of a new CFRP material to a future space reflector antennas. Three specimen types corresponding to laminating direction are reported with electrical performances. In general, the reflection and transmission characteristics will be changed according to the laminating directions of the employed materials, as listed in Table 2 showing the variations of conductivities.

In the cases of the 0° and 45° laminating directions, the characteristics of reflection and transmission approach nearly 1 and 0, respectively, with remarkable variations in the phase of the transmission coefficient.

From the reflection coefficients, it can be conjectured that the employed spaceborne antenna material proposed in this work could be considered as a conductor whose conductivity can be obtained from Section II-2.

On the contrary, the case for the 90° laminating direction results in a permittivity of 23.36-j25.91 for the used CFRP indicate a high lossy material.

IV. APPLICATION OF NEW CFRP TO THE SAR REFLECTOR ANTENNA

In order to verify the feasibility of the newly proposed M55J/RS3 material for future space applications on a SAR reflector

Table 3. Parameters and values for the SAR performance analysis

Carrier frequency (GHz)	9.6
Reflector size, D × D (m)	3 × 3
Focal length (m)	1.11
Feed beam pattern	Gaussian
Edge illumination (dB)	-12

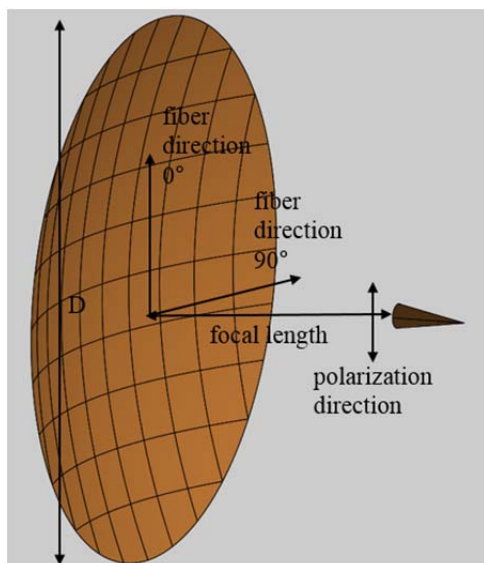


Fig. 3. The coordinates and variables of simulation for a single reflector antenna.

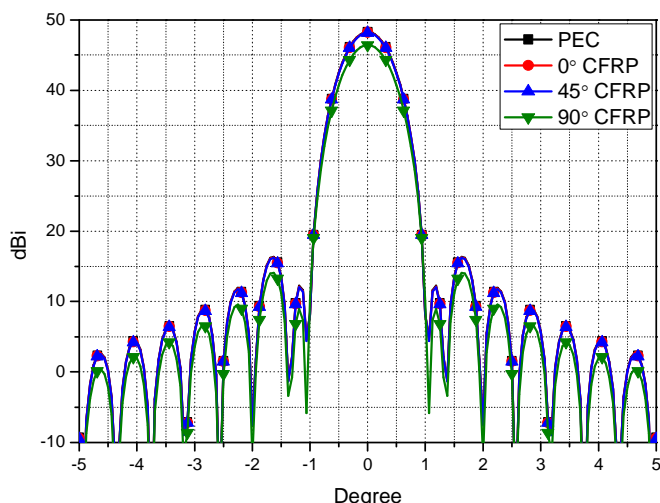


Fig. 4. The radiation pattern according to the laminating directions of the newly proposed material and ideally perfect electric conductor. PEC = perfect electric conductor, CFRP = carbon fiber reinforced polymer.

antenna, the radiation characteristics of the reflector antenna are investigated by using previously obtained effective electrical conductivity. Table 3 and Fig. 3 describe several parameters and values for the performance investigation of the SAR parabolic reflector antenna [9].

The simulation results in Fig. 4 show the radiation patterns with a sidelobe level using the commercially available PO-based software GRASP of TICRA (Copenhagen, Denmark).

It can be predicted from Fig. 4 that the gain differences in the boresight are 0.079, 0.137, and 1.886 dB according to the laminating directions 0°, 45°, and 90°, respectively.

V. CONCLUSION

This paper evaluated the feasibility of a newly developed space antenna material, M55J/RS3, for a SAR reflector antenna that must be light and highly conductive. From the electrical test results of the CFRP, it was found that electrical performances, such as reflectivity and transmission, depended on the curing method and laminating direction of the employed M55J/RS3 material. From the numerous fabrications and measurements, it was also found that the conductivity characteristics of the 0° and 45° laminating directions appeared to be better and higher than those of the 90° laminating direction. In addition, the feasibility of the newly proposed material for future space antennas was confirmed from the results in which the gain variations according to the material and ideal perfect electric conductor were too small to be ignored in the cases of the 0° and 45° laminating directions. Finally, it appears that the CFRP laminated in parallel to a single polarized direction can be applied to a future space reflector antennas requiring reduced weight and low loss characteristics.

This work was supported by the Global Surveillance Research Center (GSRC) funded by the Agency for Defense Development.

REFERENCES

- [1] European Cooperation for Space Standardization, "Space engineering," ESA Requirements and Standards Division, Noordwijk, The Netherlands, *ECSS-E-HB-32-20 Part 1A*, 2011.
- [2] J. F. Lindsey, "Space antennas from advanced composite materials," in *Proceedings of the IEEE Antennas and Propagation Society International Symposium*, Vancouver, Canada, 1985, pp. 613–616.
- [3] E. K. Pfeiffer, T. Ernst, and A. Ihle, "Highly stable lightweight antennas for Ka/Q/V-band and other telecom structure concepts," in *Proceedings of the 3rd European Conference on Antennas and Propagation*, Berlin, 2009, pp. 745–749.
- [4] L. Datashvili, N. Nathrath, H. Baier, M. Lang, D. Fasold, S. Pellegrino, O. Soykasap, L. Tan, A. Kueh, and C. Mangenot, "New concepts and reflecting materials for space borne large deployable reflector antennas," in *Proceedings of the 28th ESA Antenna Workshop on Space Antenna Systems and Technologies*, Noordwijk, The Netherlands, 2005.
- [5] K. M. Keen, "Gain-loss measurements on a carbon fibre composite reflector antenna," *Electronics Letters*, vol. 11, no. 11, pp. 234–235, May 1975.
- [6] A. M. Nicolson and G. F. Ross, "Measurement of the intrinsic properties of materials by time-domain techniques," *IEEE Transactions on Instrumentation and Measurement*, vol. 19, no. 4, pp. 377–382, Nov. 1970.
- [7] H. Rmili, J. L. Miane, H. Zangar, and T. E. Olinga, "Microwave conductivity measurements of high conductive polyaniline films," *European Physical Journal Applied Physics*, vol. 29, no. 1, pp. 65–72, Jan. 2005.
- [8] A. Galehdar, W. S. T. Rowe, K. Ghorbani, P. J. Callus, S. John, and C. H. Wang, "The effect of ply orientation on the performance of antennas in or on carbon fiber composites," *Progress in Electromagnetics Research*, vol. 116, pp. 123–136, Apr. 2011.
- [9] S. S. Yoon, J. W. Lee, T. K. Lee, and D. W. Yi, "Parameter selection procedure of parabolic reflector antenna for the optimum synthetic aperture radar performances," *Journal of Electromagnetic Engineering and Science*, vol. 13, no. 4, pp. 251–258, Dec. 2013.

Seong Sik Yoon



received the B.S. and M.S. degree in electronics, telecommunications, and computer engineering from Korea Aerospace University, Goyang, Korea, in 2010 and 2013, respectively. He is currently working toward the Ph.D. degree at the Microwave and Millimeterwave Solution Lab of Korea Aerospace University. His research interests include satellite communication antenna, radar antenna design and analysis.

His current interests are multipactor in waveguide and measurement of composite material.

Jae Wook Lee



received the B.S. degree in electronic engineering from Hanyang University, Seoul, Korea, and the M.S. and Ph.D. degrees in electrical engineering (with an emphasis in electromagnetics) from Korea Advanced Institute of Science and Technology (KAIST), Daejeon, Korea, in 1992, 1994, and 1998, respectively. From 1998 to 2004, he was a senior member in the Advanced Radio Technology Department, Radio and

Broadcasting Research Laboratory, Electronics and Telecommunications Research Institute (ETRI), Daejeon. He later joined the School of Electronics, Telecommunications and Computer Engineering, Korea Aerospace University, Korea, where he is currently a Professor. His research interests include high power amplifier design, computational electromagnetics, EMI/EMC analysis on PCB, and component design in microwave and millimeterwave.

Taek Kyung Lee




received the B.S. degree in electronic engineering from Korea University, Seoul, Korea, in 1983, and the M.S. and Ph.D. degrees in electrical engineering from the Korea Advanced Institute of Science and Technology, Seoul, in 1985 and 1990, respectively. From May 1990 to April 1991, he was a Postdoctoral Fellow with the University of Texas at Austin (under a grant from the Korea Science and Engineering Foundation). From August 1991 to February 1992, he was with the Korea Advanced Institute of Science and Technology. In March 1992, he joined the faculty of Korea Aerospace University, Goyang, Korea, where he is currently a Professor with the School of Electronics, Telecommunication, and Computer Engineering. From July 2001 to July 2002, he was an Associate Visiting Research Professor with the University of Illinois at Urbana-Champaign. His research interests include computational electromagnetics, antennas, analysis and design of microwave passive circuits, and geophysical scattering.

Jin-Ho Roh



received the B.S. degree in aerospace engineering from Korea Aerospace University, Korea, and the Ph.D. degrees in aerospace engineering from Korea Advanced Institute of Science and Technology (KAIST), Korea, in 2000 and 2006, respectively. From 2008 to 2009, he was a researcher in the Mechanical Engineering, University of Michigan, Ann Arbor, USA. He later joined the School of Aerospace and Mechanical Engineering, Korea Aerospace University, Korea, where he is currently an Associate Professor. His current research is smart composite materials and structures for the application of gossamer space structures.

Dong Woo Yi



received the B.S. degree in electronics, electric wave engineering from Chungnam University, Daejeon, Korea, and M.S. degrees in electrical engineering from Pohang University of Science and Technology in 2003, 2005, respectively. He is currently working at Agency for Defense Development. His research interests include image radar antenna design.

Hark Inn Kim



received the B.S. degree in materials engineering from Korea Aerospace University, Goyang, Korea, in 2011, respectively. He is currently working toward the M.S. degree at the Composite Materials and Structures Lab of Korea Aerospace University. His research interests include composite using shape memory polymers design and analysis.